

Handling & Process Recommendations

National Semiconductor
Application Note 2029
Martin Schnepf
June 18, 2010



Introduction

This Application Note provides recommendations for handling, storing and mounting of National Semiconductor's surface mount IC packages.

The final manufacturing yield and board level reliability are influenced by various factors and processes outside the control of the IC manufacturer. This Application Note can therefore only be used as a guideline and reference to support our customers. Due to the variety of possible board assembly materials and equipments, National Semiconductor Corporation (NSC) advises the user to consult the individual suppliers and vendors to achieve the optimum board assembly yield.

Moisture Sensitivity Level

Due to the hygroscopic nature of the plastic encapsulants, the plastic ICs absorb a certain amount of moisture. When subjecting a SMT device to reflow soldering process (e.g. infrared, convection, vapor phase), the entrapped moisture

inside the package can create excessive internal pressure resulting in delamination or even cracked package (popcorn effect).

NSC's components that are considered moisture sensitive are sealed in moisture barrier bags (MBB) together with a desiccant and a Humidity Indicator Card (HIC). National Semiconductor generally follows Industry Standards IPC/JEDEC J-STD-020 and J-STD-033 to determine the moisture sensitivity level and corresponding floor life time for NSC's plastic package types, for details on absolute maximum ratings for soldering see www.national.com/ms/MS/MS-SOLDERING.pdf.

The floor life time is the maximum time period from the opening of the MBB to the final reflow soldering process. The MSL Level and floor life time as per [Table 1](#) is provided on NSC's immediate and/or intermediate packing container label. Additionally, the MSL level and the maximum peak package temperature for National's devices can be found within the Product Folder of National's website.

TABLE 1. Moisture Sensitivity Levels (According to IPC-JEDEC J-STD-033B.1 ([Note 1](#)))

MSL Level	Floor Life (out of MBB)	
	Time	Conditions
1	Unlimited (no moisture barrier bag)	≤ 30°C / 85% RH
2	1 year	≤ 30°C / 60% RH
2A	4 weeks	≤ 30°C / 60% RH
3	168 hours	≤ 30°C / 60% RH
4	72 hours	≤ 30°C / 60% RH
5	48 hours	≤ 30°C / 60% RH
5a	24 hours	≤ 30°C / 60% RH
6	Mandatory bake before use. After bake, must be reflowed within the time limit specified on the label	≤ 30°C / 60% RH

Storage and Shelf Life

Solderability tests were conducted on components after long term storage in warehouse conditions and after exposure to accelerated aging environment. Based upon the results, NSC's shelf life of dry-packaged moisture sensitive devices inside the unopened moisture barrier bag is 3 years after original seal date when stored in an environment not exceeding 40°C / 90% RH. Component storage outside the MBB should be done in a dry storage cabinet at < 25°C and < 10% R.H. to prevent any moisture absorption.

The shelf life with regard to soldering of non dry-packed devices, i.e. MSL1, is 3 years provided the storage environment is controlled at ≤ 30°C / 85% RH.

Please be aware that e.g. bare die & wafer products have different storage conditions and limitations.

Reflow Soldering

The most popular soldering method for surface mount devices is forced convection reflow and therefore the topic of this chapter. Other possible solder processes for surface mount devices are, with restrictions, infrared reflow (IR), vapor phase and wave soldering.

It is not possible for an IC manufacturer to provide a general reflow profile recommendation for the end customer in charge of the board assembly. Reflow furnace settings depend for example on the number of heating/cooling zones, type of solder paste/flux used, board and component size as well as component density.

The actual temperature setting needs to be above the liquidus temperature (solder melting point) of the solder paste in order to form a reliable solder joint, while the upper limit is clearly defined by the maximum peak package body temperature depending on package thickness and volume as provided by IPC / JEDEC J-STD-020, see [Table 2](#) and [Table 3](#)

Note 1: Copyright IPC/JEDEC. Reproduced with permission.

TABLE 2. Maximum Peak Package Body Temperature T_p (according to IPC-JEDEC J-STD-020D) For Pb-Free Process (Note 1)

Package Thickness	Volume < 350mm ³	Volume 350-2000mm ³	Volume > 2000mm ³
<1.6 mm	260 °C	260 °C	260 °C
1.6 -2.5 mm	260 °C	250 °C	245 °C
>2.5 mm	250 °C	245 °C	245 °C


TABLE 3. For SnPb Eutectic Process (Note 1)

Package Thickness	Volume < 350mm ³	Volume ≥ 350mm ³
<2.5 mm	235 °C	220 °C
≥2.5 mm	220 °C	220 °C

NOTE: Package volume excludes external terminals (e.g., balls, bumps, lands, leads) and/or nonintegral heat sinks.

It is important to understand that the temperature profile provided within IPC/JEDEC J-STD-020 reflects the profile used for device (MSL) classification see [Figure 1](#) and [Table 4](#) with the temperature measured on the top package surface during the reflow soldering process.

The actual board assembly reflow furnace settings need to be developed separately depending on furnace characteristics and board design. The selected temperatures should not exceed the parameters used for MSL classification.

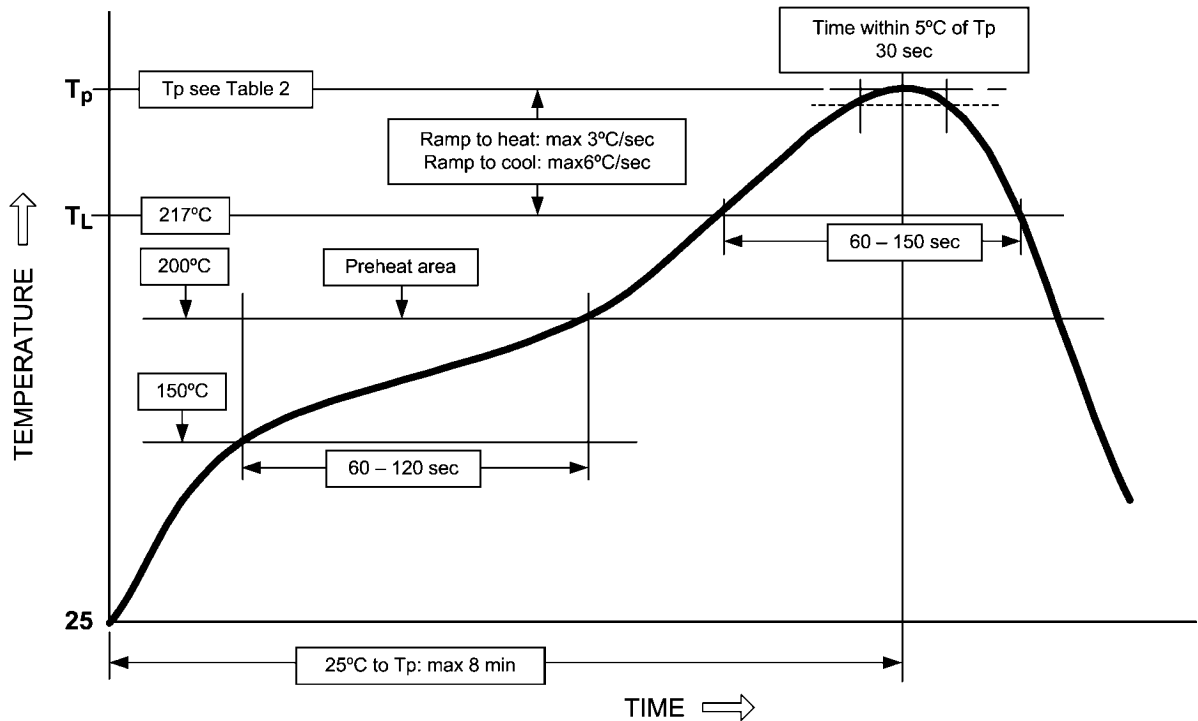

30114101

FIGURE 1. Classification Reflow Profile (peak package body temperature) for Pb-free reflow soldering


TABLE 4. Classification Reflow Profile Parameters (according to IPC-JEDEC J-STD-020D) (Note 1)

Profile Parameter	Pb-free Assembly	SnPb Assembly
Preheat Temperature range	150°C – 200°C	100°C – 150°C
Duration	60-120sec	60-120sec
Ramp-up rate	Max 3°C/sec	Max 3°C/sec
Liquidus Temperature T_L and	217°C	183°C
Time above T_L	60-150sec	60-150sec
T_p Peak Package Body Temperature	See Table 2	See Table 3
Dwell time within 5°C of at T_p	Max 30sec	Max 20sec
Ramp-down rate	Max 6°C/sec	Max 6°C/sec

Drying of Components

If the Floor Life time is exceeded or the Humidity Indicator Card indicates excessive moisture after opening the MBB (the

color change is described on the HIC card, see [Figure 2](#)), baking is required prior to the reflow process in order to remove any moisture out of the plastic package.

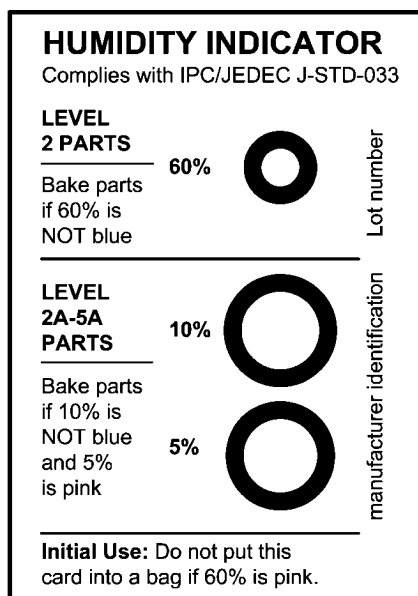

30114102

FIGURE 2. Humidity Indicator Card as per IPC/JEDEC J-STD-033B.1 ([Note 1](#))

Conditions for drying components depend on package thickness, MSL Level and baking temperature. [Table 5](#) provides an excerpt of IPC/JEDEC J-STD-033B.1 on drying mounted or unmounted SMD packages. Please note that standard packing material such as tape, reel and tubes cannot with-

stand higher baking temperatures and the components need to be taken out of the immediate shipping container. Only high temperature trays are able to withstand baking process at 125 °C.

TABLE 5. Reference Conditions for Drying Mounted and Unmounted SMD Packages (as per IPC-JEDEC J-STD-033B.1) ([Note 1](#))

Package Body	Level	Bake @ 125°C		Bake @ 90°C ≤5% RH		Bake @ 40°C ≤5% RH	
		Exceeding Floor Life by >72 h	Exceeding Floor Life by ≤72 h	Exceeding Floor Life by >72 h	Exceeding Floor Life by ≤72 h	Exceeding Floor Life by >72 h	Exceeding Floor Life by ≤72 h
Thickness ≤1.4 mm	2	5 hours	3 hours	17 hours	11 hours	8 days	5 days
	2a	7 hours	5 hours	23 hours	13 hours	9 days	7 days
	3	9 hours	7 hours	33 hours	23 hours	13 days	9 days
	4	11 hours	7 hours	37 hours	23 hours	15 days	9 days
Thickness >1.4 mm ≤2.0 mm	2	18 hours	15 hours	63 hours	2 days	25 days	20 days
	2a	21 hours	16 hours	3 days	2 days	29 days	22 days
	3	27 hours	17 hours	4 days	2 days	37 days	23 days
	4	34 hours	20 hours	5 days	3 days	47 days	28 days
Thickness >2.0 mm ≤4.5 mm	2	48 hours	48 hours	10 days	7 days	79 days	67 days
	2a	48 hours	48 hours	10 days	7 days	79 days	67 days
	3	48 hours	48 hours	10 days	8 days	79 days	67 days
	4	48 hours	48 hours	10 days	10 days	79 days	67 days

Note: For BGA package types >17x17mm, stacked die packages or packages with thickness > 4.5mm, please contact your local NSC sales representative

Repair

In case repair or even replacement of a component is needed, it is important that the temperature used for repairing, desoldering or replacing the component, needs to be selected as low as possible to avoid any damage to the adjacent components or PC board. The repair profile should be similar to the actual reflow profile, common rework tools are either hot gun or available rework machines.

In addition, depending on the MSL level of the component and if the floor life time from initial reflow soldering process to the repair process is exceeded, a baking process is required with parameters provided in IPC/JEDEC J-STD-033B.1. Otherwise, the accumulated moisture can cause damage as described in the previous chapters.

Proper handling practices are required to prevent any ESD damages during any handling of the components.

Permissions

Note 1: Copyright IPC/JEDEC. Reproduced with permission.

Notes

For more National Semiconductor product information and proven design tools, visit the following Web sites at:
www.national.com

Products		Design Support	
Amplifiers	www.national.com/amplifiers	WEBENCH® Tools	www.national.com/webench
Audio	www.national.com/audio	App Notes	www.national.com/appnotes
Clock and Timing	www.national.com/timing	Reference Designs	www.national.com/refdesigns
Data Converters	www.national.com/adac	Samples	www.national.com/samples
Interface	www.national.com/interface	Eval Boards	www.national.com/evalboards
LVDS	www.national.com/lvds	Packaging	www.national.com/packaging
Power Management	www.national.com/power	Green Compliance	www.national.com/quality/green
Switching Regulators	www.national.com/switchers	Distributors	www.national.com/contacts
LDOs	www.national.com/ldo	Quality and Reliability	www.national.com/quality
LED Lighting	www.national.com/led	Feedback/Support	www.national.com/feedback
Voltage References	www.national.com/vref	Design Made Easy	www.national.com/easy
PowerWise® Solutions	www.national.com/powerwise	Applications & Markets	www.national.com/solutions
Serial Digital Interface (SDI)	www.national.com/sdi	Mil/Aero	www.national.com/milaero
Temperature Sensors	www.national.com/tempsensors	SolarMagic™	www.national.com/solarmagic
PLL/VCO	www.national.com/wireless	PowerWise® Design University	www.national.com/training

THE CONTENTS OF THIS DOCUMENT ARE PROVIDED IN CONNECTION WITH NATIONAL SEMICONDUCTOR CORPORATION ("NATIONAL") PRODUCTS. NATIONAL MAKES NO REPRESENTATIONS OR WARRANTIES WITH RESPECT TO THE ACCURACY OR COMPLETENESS OF THE CONTENTS OF THIS PUBLICATION AND RESERVES THE RIGHT TO MAKE CHANGES TO SPECIFICATIONS AND PRODUCT DESCRIPTIONS AT ANY TIME WITHOUT NOTICE. NO LICENSE, WHETHER EXPRESS, IMPLIED, ARISING BY ESTOPPEL OR OTHERWISE, TO ANY INTELLECTUAL PROPERTY RIGHTS IS GRANTED BY THIS DOCUMENT.

TESTING AND OTHER QUALITY CONTROLS ARE USED TO THE EXTENT NATIONAL DEEMS NECESSARY TO SUPPORT NATIONAL'S PRODUCT WARRANTY. EXCEPT WHERE MANDATED BY GOVERNMENT REQUIREMENTS, TESTING OF ALL PARAMETERS OF EACH PRODUCT IS NOT NECESSARILY PERFORMED. NATIONAL ASSUMES NO LIABILITY FOR APPLICATIONS ASSISTANCE OR BUYER PRODUCT DESIGN. BUYERS ARE RESPONSIBLE FOR THEIR PRODUCTS AND APPLICATIONS USING NATIONAL COMPONENTS. PRIOR TO USING OR DISTRIBUTING ANY PRODUCTS THAT INCLUDE NATIONAL COMPONENTS, BUYERS SHOULD PROVIDE ADEQUATE DESIGN, TESTING AND OPERATING SAFEGUARDS.

EXCEPT AS PROVIDED IN NATIONAL'S TERMS AND CONDITIONS OF SALE FOR SUCH PRODUCTS, NATIONAL ASSUMES NO LIABILITY WHATSOEVER, AND NATIONAL DISCLAIMS ANY EXPRESS OR IMPLIED WARRANTY RELATING TO THE SALE AND/OR USE OF NATIONAL PRODUCTS INCLUDING LIABILITY OR WARRANTIES RELATING TO FITNESS FOR A PARTICULAR PURPOSE, MERCHANTABILITY, OR INFRINGEMENT OF ANY PATENT, COPYRIGHT OR OTHER INTELLECTUAL PROPERTY RIGHT.

LIFE SUPPORT POLICY

NATIONAL'S PRODUCTS ARE NOT AUTHORIZED FOR USE AS CRITICAL COMPONENTS IN LIFE SUPPORT DEVICES OR SYSTEMS WITHOUT THE EXPRESS PRIOR WRITTEN APPROVAL OF THE CHIEF EXECUTIVE OFFICER AND GENERAL COUNSEL OF NATIONAL SEMICONDUCTOR CORPORATION. As used herein:

Life support devices or systems are devices which (a) are intended for surgical implant into the body, or (b) support or sustain life and whose failure to perform when properly used in accordance with instructions for use provided in the labeling can be reasonably expected to result in a significant injury to the user. A critical component is any component in a life support device or system whose failure to perform can be reasonably expected to cause the failure of the life support device or system or to affect its safety or effectiveness.

National Semiconductor and the National Semiconductor logo are registered trademarks of National Semiconductor Corporation. All other brand or product names may be trademarks or registered trademarks of their respective holders.

Copyright© 2010 National Semiconductor Corporation

For the most current product information visit us at www.national.com



**National Semiconductor
Americas Technical
Support Center**
Email: support@nsc.com
Tel: 1-800-272-9959

**National Semiconductor Europe
Technical Support Center**
Email: europe.support@nsc.com

**National Semiconductor Asia
Pacific Technical Support Center**
Email: ap.support@nsc.com

**National Semiconductor Japan
Technical Support Center**
Email: jpn.feedback@nsc.com